Engineering Conferences International ECI Digital Archives

Nanomechanical Testing in Materials Research and Development V

Proceedings

Fall 10-4-2015

Effects of lithiation on the fracture toughness and mechanical properties of LiMn2O4 cathode battery materials

Marco Sebastiani *Roma TRE University,* marco.sebastiani@uniroma3.it

K.E. Johanns *TU Darmstadt*

Hugues Amanieu Bosch

G.M. Pharr Oak Ridge Laboratory

Follow this and additional works at: http://dc.engconfintl.org/nanomechtest_v Part of the <u>Materials Science and Engineering Commons</u>

Recommended Citation

Marco Sebastiani, K.E. Johanns, Hugues Amanieu, and G.M. Pharr, "Effects of lithiation on the fracture toughness and mechanical properties of LiMn2O4 cathode battery materials" in "Nanomechanical Testing in Materials Research and Development V", Dr. Marc Legros, CEMES-CNRS, France Eds, ECI Symposium Series, (2015). http://dc.engconfintl.org/nanomechtest_v/89

This Abstract is brought to you for free and open access by the Proceedings at ECI Digital Archives. It has been accepted for inclusion in Nanomechanical Testing in Materials Research and Development V by an authorized administrator of ECI Digital Archives. For more information, please contact franco@bepress.com.

Effects of lithiation on the fracture toughness and mechanical properties of LiMn2O4 cathode battery materials

M. Sebastiani*1, K. E. Johanns², Hugues-Yanis Amanieu^{3,4}, G. M. Pharr^{5,6}

¹ Roma TRE University, Engineering Department, Italy

² Department of Materials Science, TU Darmstadt, D-64287 Darmstadt, Germany

³ Robert Bosch GmbH, Robert-Bosch-Platz 1, 70839 Gerlingen-Schillerhoehe, Germany

⁴ Institute for Materials Science, Center for Nanointegration Duisburg-Essen (CENIDE), University of Duisburg-Essen,


Universitätsstr. 15, 45141 Essen, Germany

⁵ Department of Materials Science & Engineering, The University of Tennessee, Knoxville, TN, USA


⁶ Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN, USA

*corresponding author: <u>marco.sebastiani@uniroma3.it</u>

The micro-pillar splitting method has been used to assess the influence of lithiation on the fracture toughness of Li_xMn₂O₄ micro-particles used as cathode materials in lithium ion battery composites. The materials under investigation consisted of hard LiMn2O4 particles embedded in a soft and compliant epoxy matrix to form the composite electrode. Five different samples were extracted from commercial battery cells at different states of charge (SoC% = 0-20-50-75-100%). These correspond to different lithium concentrations in the particles, as measured by inductively coupled plasma optical emission spectrometry (ICP-OES). Experimental results from the pillar splitting experiments show a significant effect of the SoC%, and therefore the lithiation level, on the fracture toughness and failure mechanisms of the Li_xMn₂O₄ particles. Specifically, the toughness of the fully charged electrodes (de-lithiated material) is much lower that the fully discharged electrodes. SEM observation of split pillars (see figure) confirms a significant change in toughness of the materials as a function of the lithium concentration in the particles. The results compare well with recent investigations where a loss in ductility of electrode materials has been observed after de-lithiation. This suggests that a knowledge of the changes in toughness of the materials may be extremely important for prediction of in-service damage of the electrodes due to diffusion-induced stress during charge/discharge cycles. An analysis of pillar splitting for a hard film on a compliant substrate material shows that the critical load for splitting is relatively insensitive to the substrate compliance for a large range of material properties. This ensures a correct estimation of the critical splitting load in the case of the composite materials studied in this investigation.

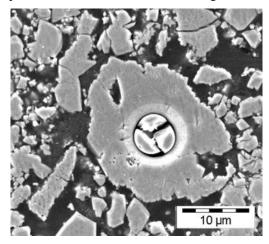

Fully charged electrode (very brittle failure – low Kc)

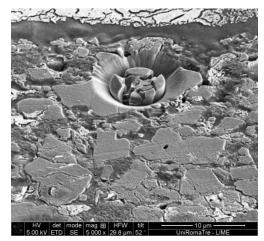

Fully discharged electrode (damage tolerant behavior – at least 30% higher Kc)